

# GEOSTATS PTY LTD

Mining Industry Consultants  
Reference Material Manufacture and Sales

## Certified Gold Reference Material Product Code

# G910-4


## Certified Control Values

### 50 gram Fire Assay

Gold Grade 16.92 ppm  
Standard Deviation 0.72 ppm  
Confidence Interval +/- 0.121 ppm

### Aqua Regia Digest

Gold Grade 16.62 ppm  
Standard Deviation 0.87 ppm  
Confidence Interval +/- 0.223 ppm

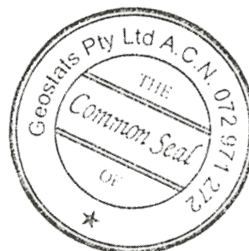

## CRM Details

<u>Control Statistic Details</u>	<u>Neutron Activation Analysis Results (ppm, unless otherwise noted)</u>	<u>Major Elements by Fusion / XRF (%)</u>	
Control statistics were produced from results accumulated in the October-2010 round robin. A total of 142 fire assay results and 62 results from an aqua regia technique were used to certify this material.	Antimony 0.104	Fe	4.98
	Arsenic 0.548	SiO <sub>2</sub>	61.92
	Barium 471	Al <sub>2</sub> O <sub>3</sub>	15.04
	Bromine 0.794	TiO <sub>2</sub>	1.033
	Cadmium <5	MnO	0.1
	Caesium 3.01	CaO	5.54
	Calcium (%) nr	P	0.055
	Cerium 20.2	S	0.026
	Chromium 148	MgO	2.89
	Cobalt 21.8	K <sub>2</sub> O	2.28
	Europium <1	Na <sub>2</sub> O	3.541
	Gold (ppb) 18500	LOI1000	0.34
	Hafnium 3.84	Neutron Activation Analyses and Fusion / XRF Analyses are single results and are indicative only. These are provided for matrix identification purposes.  'nr': Not Reported	
	Iridium (ppb) <10		
	Iron (%) 5.2		
	Lanthanum 23.3		
	Lutetium 0.409		
	Mercury nr		
	Molybdenum 49.4		
	Neodymium nr		
	Nickel 23.1		
	Potassium (%) nr		
	Rubidium 117		
	Samarium 4.38		
	Scandium 18.7		
	Selenium <5		
	Silver 23.5		
	Sodium (%) 2.64		
	Strontium nr		
	Tantalum 1.27		
	Tellurium <10		
	Terbium 0.814		
	Thorium 15.3		
	Tin <100		
	Tungsten 2.18		
	Uranium 7.3		
	Ytterbium 2.72		
	Zinc 82		
	Zirconium <200		
<u>Material Description</u> This material is described as a High Grade mine ore low sulphide.			
<u>Colour Designation (ISCC-NBS, SP440)</u> This material is medium light gray in colour.			
<u>Usage</u> This product is for use in the mining industry as a reference material for monitoring and testing the accuracy of laboratory assaying.			
<u>Preparation and Packaging</u> All CRMs are dried in an oven for a minimum of 12 hours at 110°C. The dry material is then pulverised to better than 75 micron (nominal mean of 45 micron) using an air classifier. The material is then homogenised and stored in a sealed, stable container ready for final packaging.  Materials are statistically sampled from stores, then packaged into either heat sealed, air tight, plastic pulp packets or screw top sealed plastic containers ready for distribution. All packaging has been chosen to ensure minimal contamination from outside sources during shipment, use and storage.			
<u>Assay Testwork</u> All standards are tested thoroughly in the Geostats bi-annual laboratory survey. This involves assaying by multiple laboratories from around the world. Results are compiled into a comprehensive report detailing statistics for each standard. Assay distributions are checked and processed statistically, producing monitoring statistics for these standards. Materials are tested regularly to ensure stability and homogeneity.			
<u>Stability</u> This product remains stable in its original packaging, away from direct sunlight.			
<u>Material Safety</u> This product is not hazardous and non-toxic.			

20 Hines Road, O'Connor, Western Australia 6163

Phone : +61 8 9314 2566, Fax : +61 8 9314 3699

e-mail : pjh@geostats.com.au, srr@geostats.com.au

Website <http://www.geostats.com.au>

G910-4

Geostats Pty Ltd, Certified Gold Reference Material, Product Code: